



Original Research

Synthesis by gamma irradiation of hyaluronic acid-polyvinyl alcohol hydrogel for biomedical applications

Fernanda Kamila Godoy-Alvarez¹, Maykel González-Torres², David M. Giraldo-Gomez^{3,4}, Roberto Sánchez-Sánchez⁵, Mario A. Pérez-Díaz⁵, Manuel González-Del Carmen⁶, Gabriela Figueroa-González⁷, Octavio D. Reyes-Hernández⁸, Javad Sharifi-Rad^{9,10}, Hernán Cortés¹¹, María Luisa Del Prado-Audelo^{1,12*}, Gerardo Leyva-Gómez^{1*}

¹ Departamento de Farmacia, Facultad de Química, Universidad Nacional Autónoma de México, Ciudad de México, 04510, Mexico

² CONACyT-Laboratorio de Biotecnología, Instituto Nacional de Rehabilitación Luis Guillermo Ibarra Ibarra, Ciudad de México, 14389, Mexico

³ Departamento de Biología Celular y Tisular, Facultad de Medicina, Universidad Nacional Autónoma de México, Ciudad de México, 04510, Mexico

⁴ Unidad de Microscopía, Facultad de Medicina, Universidad Nacional Autónoma de México, Ciudad de México, 04510, Mexico

⁵ Unidad de Ingeniería de Tejidos Terapia Celular y Medicina Regenerativa, Instituto Nacional de Rehabilitación Luis Guillermo Ibarra Ibarra (INR-LGII), Ciudad de México, 14389, Mexico

⁶ Facultad de Medicina, Universidad Veracruzana, Ciudad Mendoza, 94740, Veracruz, Mexico

⁷ Laboratorio de Farmacogenética, UMIEZ, Facultad de Estudios Superiores Zaragoza, Universidad Nacional Autónoma de México, Ciudad de México, 09230, Mexico

⁸ Laboratorio de Biología Molecular del Cáncer, UMIEZ, Facultad de Estudios Superiores Zaragoza, Universidad Nacional Autónoma de México, Ciudad de México 09230, Mexico

⁹ Phytochemistry Research Center, Shahid Beheshti University of Medical Sciences, Tehran, Iran

¹⁰ Facultad de Medicina, Universidad del Azuay, Cuenca, Ecuador

¹¹ Laboratorio de Medicina Genómica, Departamento de Genómica, Instituto Nacional de Rehabilitación-Luis Guillermo Ibarra Ibarra, Ciudad de México, 14389, Mexico

¹² Escuela de Ingeniería y Ciencias, Departamento de Bioingeniería, Tecnológico de Monterrey Campus Ciudad de México, Ciudad de México, 14380, Mexico

*Correspondence to: luisa.delpradoa@gmail.com; leyva@quimica.unam.mx

Received August 25, 2020; Accepted November 12, 2020; Published January 31, 2021

Doi: <http://dx.doi.org/10.14715/cmb/2021.67.1.9>

Copyright: © 2021 by the C.M.B. Association. All rights reserved.

Abstract: Hyaluronic acid (HA) is one of the most attractive natural polymers employed in biomaterials with biological applications. This polysaccharide is found in different tissues of the body because it is a natural component of the extracellular matrix; furthermore, it has crucial functions in cell growth, migration, and differentiation. Since its biological characteristics, HA has been utilized for the new biomaterial's development for tissue engineering, such as hydrogels. These hydrophilic macromolecular networks have gained significant attention due to their unique properties, making them potential candidates to be applied in biomedical fields. Different mechanisms to obtain hydrogels have been described. However, the research of new non-toxic methods has been growing in recent years. In this study, we prepared a new hydrogel of HA and polyvinyl alcohol by the cost-effective technique of cross-linking by gamma irradiation. The hydrogel was elaborated for the first time and was characterized by several methods such as Fourier Transform Infrared Spectroscopy, Differential Scanning Calorimetry, Thermogravimetric Analysis, and Scanning Electron Microscopy. Likewise, we evaluated the cytotoxicity of the biomaterial and its influence on cell migration in human fibroblasts. Furthermore, we provide preliminary evidence of the wound closure effect in a cellular wound model. The novel hydrogel offers an increase of HA stability with the potential to expand the useful life of HA in its different medical applications.

Key words: Biomaterial; Hyaluronic acid; Poly(vinyl) alcohol; Hydrogel; Gamma irradiation; Polymers.

Introduction

Hydrogels are semi-solid systems formed by the cross-linking of natural and synthetic polymers (1,2). They have a three-dimensional network structure under covalent or non-covalent bonds in the liquid medium that can retain a large amount of water in its swollen state (3). The properties of hydrogels resemble those of biological tissues, resulting in excellent biocompatibility (4). In this regard, hyaluronic acid (HA) is a natural polymer widely studied and applied as a hydrogel constituent for biomedical applications (5). It is a

component of the Extracellular Matrix (ECM), which is involved in regulation of diverse cellular responses, mainly in fibroblasts and smooth cells (6,7). These functions are primarily mediated by interactions with three classes of cell surface receptors: a) CD44 (a membrane glycoprotein), b) receptor for hyaluronate-mediated motility (RHAMM), and c) Intercellular adhesion molecule 1 (ICAM- 1). The binding to these receptors triggers different intracellular signaling pathways that control cellular biological processes such as angiogenesis, cell migration, cell proliferation, cell aggregation, and cell adhesion to ECM components (8,9). On the

other hand, polyvinyl alcohol (PVA) is a linear synthetic polymer that presents suitable biological properties. It is used frequently as a polymeric membrane material for wound dressings and coverings (10). However, its use is restricted due to its limited hydrophilicity, resulting in insufficient elasticity and rigid structure (11). Therefore, to improve its mechanical characteristics and biological properties, it has been merged with some natural polymers (12).

In this study, HA was cross-linked with PVA through gamma irradiation. This cross-linking method is considered a cost-effective, safe, and straightforward process because no toxic chemical agents are employed (13). The cross-linking by gamma irradiation of aqueous polymer solutions is carried out through the linear carbon radicals formation along the skeleton and the construction of a network by the recombination of polymer radicals (14,15). The obtained biomaterial was characterized to evaluate its chemical interactions, thermal behavior, and morphology. The cytotoxicity of the biomaterial and its influence on cell migration were assessed in human dermal fibroblasts. According to the results, the new and versatile hydrogel could be applied in different fields such as tissue engineering or drug delivery systems.

Materials and Methods

Materials

HA was purchased from Sigma-Aldrich® Chemical Co. (St. Louis, MO, USA) (Mw reported ~30,000 Dalton). PVA was obtained from Merck (Mowiol® 4-88, CAS 9002-89-5). The LIVE/DEAD Viability/Cytotoxicity for Mammalian Cells kit was acquired from ThermoFisher Scientific® (Carlsbad, CA, USA).

Sample preparation

Preparation of the Hyaluronic Acid + PVA solution (HA+PVA)

The PVA solution at 5% (w/v) was prepared in water at 90 °C by magnetic stirring. This solution (200 mL) was added to 50 mL of HA (0.02% w/v) in a glass container to obtain a homogeneous mixture.

Synthesis of Hyaluronic Acid-PVA hydrogel (HA-PVA)

The solution of HA and PVA obtained was subjected to gamma irradiation with an absorbed dose of 25 kGy, using a ⁶⁰Co source in the presence of air. This procedure was carried out through Fricke dosimeter equipment, with a dose ratio of 8.5 kGy h⁻¹.

Physicochemical characterization

HA-PVP hydrogel was freeze-dried at -49°C, with a pressure of 0.05 mBar for 24 h. In order to evaluate the structural changes triggered by the radiation, the lyophilized samples were characterized by Fourier Transform Infrared Spectroscopy (FT-IR), Differential Scanning Calorimetry (DSC), Thermogravimetric Analysis (TGA), and Scanning Electron Microscopy (SEM). FT-IR spectra were recorded on an FTIR Nicolet 6700 spectrophotometer (Thermo Fisher Scientific®, USA), and the samples were scanned in the range of

4,000 and 400 cm⁻¹. The TGA tests were carried out on a Hi-Res TGA 2950 Thermogravimetric Analyzer (Modulated TA Instruments®, DE, USA). The samples were analyzed from room temperature to 500 °C. The DSC tests were performed from -50 °C to 350 °C with the DSC 2910 (Modulated TA Instruments®, DE, USA). The heating ratio of 10 °C/min under a nitrogen atmosphere was utilized for both techniques. The morphology was analyzed using an EVO MA10 Microscopy (Zeiss®, Germany).

Biological characterization

The biocompatibility of the hydrogel and its performance in a wound model was evaluated to analyze changes in its biological behavior due to the radiation process. Dermal fibroblasts were isolated from human skin after aesthetic surgeries and obtaining the signed informed consent. We used calcein and Ethidium homodimer 1 (EthD-1) to determine cell viability through the LIVE/DEAD Viability/Cytotoxicity for Mammalian Cells kit. Photographs were taken using an epifluorescence microscope AxioObserver (Zeiss®, Germany). The number of live (calcein-positive) and dead (EthD-1-positive) cells were counted employing ImageJ software. For the wound-healing assay, fibroblasts were cultured until confluence in 24-well culture dishes (Corning®, USA). Then, a scratch was performed using a 1-mL micropipette tip. Cells were cultured with the hydrogel (1, 2, 4, and 8%) in addition to the control condition (culture medium) and the vehicle condition (PBS, GIBCO®, USA). The closure of the wound was analyzed for two days, and the distance between the cells was calculated using ImageJ software.

Statistical analysis

Statistical analysis was performed by ANOVA with a Tukey posthoc test, and $p < 0.05$ was considered significant. All data were analyzed using Graph Pad Prism Software version 7.05 (San Diego, CA, USA).

Results

Physicochemical Characterization

The FTIR spectra for HA and PVA (Fig. 1a and 1b, respectively) presented the characteristic bands of these excipients (11,16,17). For the HA spectrum (line a), the bending and tension bond of the N-H group were observed at 3,291 cm⁻¹ and 2,940 cm⁻¹, respectively. Furthermore, the carbonyl group (C=O) of HA was visible at 1,600 cm⁻¹. Simultaneously, the bands of acid were presented with the asymmetric stretching and symmetric vibrations of the COO⁻ group at 1,406 cm⁻¹ coupled with the CO- bridge and the flexion of the group COH, observed at 1,149 cm⁻¹ and 1,034 cm⁻¹, respectively (17,18).

Concerning the PVA (line b), the characteristic large band of absorption corresponding to the tension of the intermolecular and intramolecular hydrogen bonds of the hydroxyl group (O-H) was observed at 3,300 cm⁻¹. Likewise, the stretching of the carbonyl group of the non-hydrolyzed acetate ion was observed at 1,730 cm⁻¹ (16). The HA+PVA and HA-PVA spectra presented mainly the PVA behavior.

The thermogravimetric analysis of the samples is depicted in Fig. 2. For the excipients (line a and line b), the

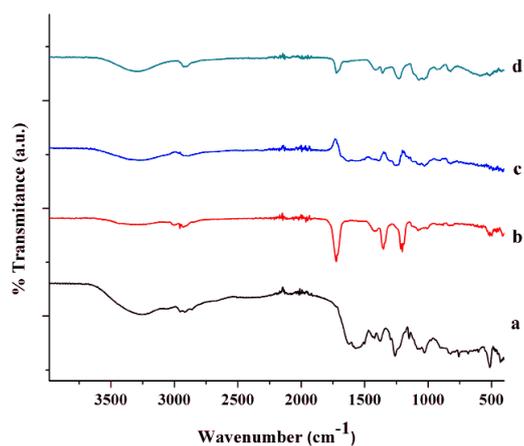


Figure 1. FT-IR spectra of the components of the biopolymer: (a) Hyaluronic Acid (HA); (b) Polyvinyl Alcohol (PVA); (c) HA+PVA, and (d) HA-PVA.

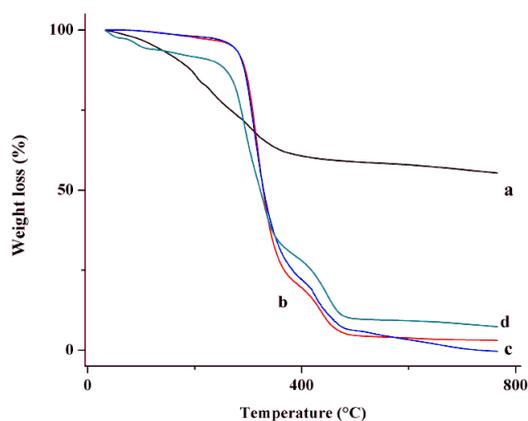


Figure 2. TGA of the components of the biopolymer: (a) Hyaluronic Acid (HA); (b) Polyvinyl Alcohol (PVA); (c) HA+PVA, and (d) HA-PVA.

Table 1. Differential Scanning Calorimetry (DSC) results.

| Sample | Tm1 (°C) | Tm2 (°C) | Tm3 (°C) |
|--------|----------|----------|----------|
| HA | 46.0 | 136.8 | 210.7 |
| PVA | 51.8 | 192.4 | 324.6 |
| HA+PVA | 51.8 | 194.5 | 326.0 |
| HA-PVA | 58.6 | 181.4 | 298.9 |

characteristic thermal behavior was observed (16,17). In thermograms of PVA, HA+PVA, and HA-PVA (lines b, c, and d, respectively), a weight loss in the range of 300 °C to 500 °C was found. The drastic drop was mainly due to the decomposition of the organic components, as previously described for HA hydrogels (18). A difference of approximately 7% in weight was observed at the test end between HA+PVA and HA-PVA (lines c and d, respectively). Moreover, Table 1 details the DSC results; a substantial left peak shift is seen on Tm2 and Tm3 in HA-PVA analysis compared to the excipients and the HA+PVA behavior, suggesting a chemical interaction between the components triggered by the irradiation.

The morphology of the biomaterial was evaluated by SEM analysis (Fig. 3). As can be observed, the hydrogel presented a porous microstructure. The interconnected

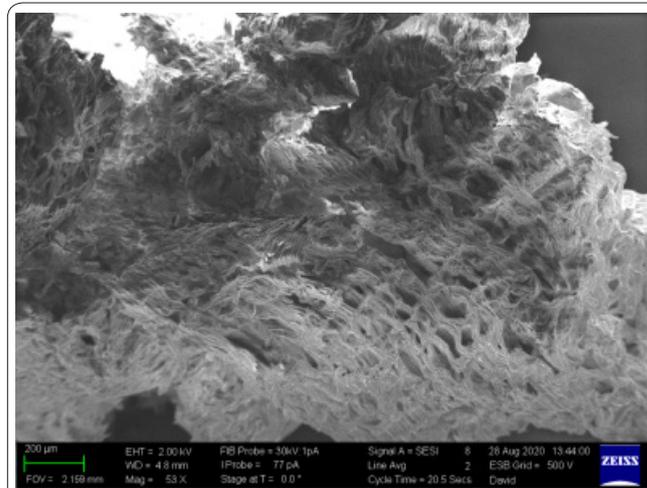


Figure 3. SEM image of the HA-PVA hydrogel microstructure. Scale bar: 200 μm .

flat pores had a diameter between 100 and 200 μm .

Biological characterization

This study evaluated the viability of dermal fibroblasts in the presence of different concentrations of the hydrogel (Fig. 4.A). All treatments were not cytotoxic due to the percentage of viability in all cases was very close to 100% (Fig 4.C). Statistical analysis revealed that none treatment with HA-PVA samples affected cell viability. Remarkably, in all conditions, dermal fibroblasts presented their classical morphology, suggesting that the hydrogel did not affect cell adhesion.

In the wound-healing assay (Fig 4.B), the cell migration velocity was nearly the same in all the treatments (1%, 2%, 4, and 8%), even in control. The vehicle (Vh) showed a slight delay in closing; however, it was not significant (Fig. 4D). On the first day of analysis, the treatment of 1% of the biomaterial presented a slight increase in migration; however, it was not significant. On the second day of the analysis, all the experiments showed a close wound.

Discussion

Physicochemical characterization

The FTIR spectra revealed an abundance of intermolecular and intramolecular bonds of O-H in the band at 3,300 cm^{-1} on the spectra of HA+PVA and HA-PVA (Figure 1 line c and line d, respectively), suggesting a high affinity for an aquatic environment and the formation of free radicals. Furthermore, these bonds could provide high hydrophobicity to the new biomaterial, obtaining a material that retains a large amount of liquid. This characteristic is required in terms of compatibility with blood and biological fluids (19). Therefore, an interaction between HA and PVA was exhibited due to the presence of covalent bonds between the polymers, and we observed the decrease in the intensity of the C=O. Besides, in HA-PVA spectrum, the amine bands are present; however, the bands related to PVA revealed a decrement in intensity, indicating an interaction between HA and PVA. The last could be supported by expecting that the dominant interactions were the hydrogen bonds between the hydroxyl groups of PVA and the amino groups of HA. This conclusion generated the idea of the possible mechanism of interaction between

respect, we observed that the new biomaterial presented an interconnected porous network with elongated pores distributed into the structure (Fig. 3). This porous structure was owing to the gradual polymerization reaction and the cross-linking density of the hydrogels (27), allowing an ordered matrix that helps the proper infiltration of living cells, gases, nutrients, cell factors, and waste products diffusion (28). Hence, this hydrogel could be applied as a scaffold in tissue engineering and as a wound dressing

Biological characterization

We evaluated cell viability and migration to analyze the effect of different concentrations of the new material (Fig. 4). The calcein/EthD-1 assays were performed at different concentrations of HA–PVA samples to analyze cell viability, evaluating the fluorescence of the cells. We found abundant living cells under all conditions. Furthermore, the dermal fibroblasts exhibited their classical morphology in the biomaterial presence. The morphology is related to the cell adhesion, which is reported as meaningful communication with the surrounding environment, indicating strong vitality (18). Thus, the mentioned above suggests that the treatments did not affect cell viability; therefore, they did not affect cell adhesion (29). Based on these results, the hydrogels may be considered a non-toxic biomaterial that does not affect the morphology and physiology of the cells; thus, these could be used in future models because they allow cell viability.

The wound-healing assay, an *in vitro* standard test representative of separation in a wound, was carried out to study the behavior that exists regarding the migration of cells in the presence of the biomaterial. After creating a linear scratch on the dermal fibroblast cell monolayer, the cells started to recruit from the edges of the space to close the gap at a measurable rate from an area with higher cell density to a region with lower cell density (30,31).

It is well-known that the HA is implicated in cell migration, which is essential for wound healing (35,36) and scar-free healing (37). Furthermore, it has been reported that the treatment of dermal wounds with HA hydrogels promotes cellular migration and proliferation, indicating the pathway of interaction with the other cells (32,33). We found a complete migration of cells for all HA–PVA concentrations, revealing that the hydrogel provides adequate cell migration (Figures 4B and 4D). Also, the 4% HA–PVA treatment demonstrated a slight increase in fibroblast migration, accelerating the closure of the wound model. These findings suggest that the biochemical interaction of the HA–PVA hydrogel could activate signaling pathways similar to HA when bonded to CD44 and RHAMM receptors (34). Those properties suggest the potential biomedical application of the new biomaterial as a wound dressing that could help in the re-epithelialization and healing of wounds to optimize the repair skin process (17).

Therefore, we developed a unique and multipurpose novel material based on HA and PVA, which exhibits intrinsic characteristics that make it a versatile biomaterial with the same biological properties and higher HA stability; this is attractive because it can increase the shelf life of HA applications. Moreover, the HA–PVA

hydrogel increases the potential applications of HA in different biomedical and pharmaceutical fields.

A new HA- and PVA-based hydrogel was successfully obtained by gamma irradiation. Additionally, this safe and effective technique provides sterility to the irradiated material. The novel hydrogel presented a porous network structure and possessed a synergistic mixture of the attractive characteristics of the individual materials. Both the biological activity of the HA and the well-studied features of PVA were maintained. The biological properties were evaluated in cell cultures of human dermal fibroblasts, obtaining a non-toxic material that promotes cell viability and cell migration. The biocompatibility, high porosity, and thermal stability characteristics render this new hydrogel an alternative biomaterial to be applied in the tissue engineering field with excellent stability and the potential to increase the useful life of HA in its different medical applications.

Acknowledgements

This research was funded by CONACYT A1-S-15759 to Gerardo Leyva-Gómez. The authors thank Miguel Ángel Canseco-Martínez for the help of FTIR analysis, Karla Eriseth Reyes-Morales, for her technical assistance with thermal tests, Ana Bobadilla-Valencia for her technical aid with nitrogen handling used in the experimental setting. And to Elba Carrasco Ramirez, Irma Elena López Martínez, and Ivonne Grisel Sánchez Cervantes from the Microscopy Core Facility from the School of Medicine at the UNAM for their technical assistance with microscopy assessment.

Conflicts of interest

There are no conflicts to declare.

References

1. Feksa LR, Troian EA, Muller CD, Viegas F, Machado AB, Rech VC. Hydrogels for biomedical applications. *Nanostructures Eng Cells, Tissues Organs From Des to Appl.* 2018;64:403–38.
2. Leyva-Gómez G, Santillan-Reyes E, Lima E, Madrid-Martínez A, Kröttsch E, Quintanar-Guerrero D, et al. A novel hydrogel of poloxamer 407 and chitosan obtained by gamma irradiation exhibits physicochemical properties for wound management. *Mater Sci Eng C.* 2017;74:36–46.
3. Gupta A, Kowalczyk M, Heaselgrave W, Britland ST, Martin C, Radecka I. The production and application of hydrogels for wound management: A review. *Eur Polym J.* 2019;111:134–51.
4. Buwalda SJ, Boere KWM, Dijkstra PJ, Feijen J, Vermonden T, Hennink WE. Hydrogels in a historical perspective: From simple networks to smart materials. *J Control Release.* 2014;190:254–73.
5. Cortes H, Caballero-Floran I, Mendoza-Muñoz N, Cordova-Villanueva E, Escutia-Guadarrama L, Figueroa-Gonzalez G, et al. Hyaluronic acid in wound dressings. *Cell Mol Biol.* 2020;66(4):192–9.
6. Vigetti D, Karousou E, Viola M, Deleonibus S, De Luca G, Passi A. Hyaluronan: Biosynthesis and signaling. *Biochim Biophys Acta.* 2014;1840:2452–9.
7. Cyphert JM, Trempus CS, Garantziotis S. Size Matters: Molecular Weight Specificity of Hyaluronan Effects in Cell Biology. *Int J Cell Biol.* 2015;1–8.
8. Larrañeta E, Henry M, Irwin NJ, Trotter J, Perminova AA, Donnelly RF. Synthesis and characterization of hyaluronic acid hydrogels crosslinked using a solvent-free process for potential biomedical applications. *Carbohydr Polym.* 2018;181(November

2017):1194–205.

9. Wolf KJ, Kumar S. Hyaluronic Acid: Incorporating the Bio into the Material. *ACS Biomater Sci Eng.* 2019;5(8):3753–65.

10. Teixeira MA, Amorim MTP, Felgueiras HP. Poly(vinyl alcohol)-based nanofibrous electrospun scaffolds for tissue engineering applications. *Polymers (Basel).* 2020;12(1):7.

11. Teodorescu M, Bercea M, Morariu S. Biomaterials of PVA and PVP in medical and pharmaceutical applications: Perspectives and challenges. *Biotechnol Adv.* 2018;37:109–31.

12. Kamoun EA, Chen X, Mohy Eldin MS, Kenawy E-RS, Journal A. Crosslinked poly(vinyl alcohol) hydrogels for wound dressing applications: A review of remarkably blended polymers. *Arab J Chem.* 2015;8:1–14.

13. Türker NS, Özer AY, Kutlu B, Nohutcu R, Sungur A, Bilgili H, et al. The effect of gamma radiation sterilization on dental biomaterials. *Tissue Eng Regen Med.* 2014;11(5):341–9.

14. Zhao L, Gwon HJ, Lim YM, Nho YC, Kim SY. Gamma ray-induced synthesis of hyaluronic acid/chondroitin sulfate-based hydrogels for biomedical applications. *Radiat Phys Chem.* 2015;106:404–12.

15. González Torres M, Cerna Cortez J, Balam Muñoz Soto R, Ríos Perez A, Pfeiffer H, Leyva Gómez G, et al. Synthesis of gamma radiation-induced PEGylated cisplatin for cancer treatment. *RSC Adv.* 2018;8(60):34718–25.

16. Liu J, Chang MJ, Du HL. Facile preparation of cross-linked porous poly(vinyl alcohol) nanofibers by electrospinning. *Mater Lett.* 2016;183:318–21.

17. Ahire JJ, Robertson D, Neveling DP, Reenen AJ Van, Dicks LMT. Hyaluronic acid-coated poly(D,L-lactide) (PDLLA) nanofibers prepared by electrospinning and coating. *R Soc Chem.* 2016;6:34791–6.

18. Yang W, Xu H, Lan Y, Zhu Q, Liu Y, Huang S, et al. Preparation and characterisation of a novel silk fibroin/hyaluronic acid/sodium alginate scaffold for skin repair. *Int J Biol Macromol [Internet].* 2019;130:58–67. Available from: <https://doi.org/10.1016/j.ijbiomac.2019.02.120>

19. Rezvani Ghomi E, Khalili S, Nouri Khorasani S, Esmaeely Neisiany R, Ramakrishna S. Wound dressings: Current advances and future directions. *J Appl Polym Sci.* 2019;136(27):1–12.

20. Belaidi A, Guettari M, Tajouri T. Gamma-ray irradiation-induced variations in structural and electrical properties of PVP neutral polymer in water. *J Radioanal Nucl Chem.* 2019;322(2):869–77.

21. Zhai P, Peng X, Li B, Liu Y, Sun H, Li X. The application of hyaluronic acid in bone regeneration. *Int J Biol Macromol.* 2020;151:1224–39.

22. Eisa WH, Abdel-Moneam YK, Shabaka AA, Elhameed A, Hosam M. In situ approach induced growth of highly monodispersed Ag nanoparticles within free standing PVA/PVP films. *Spectrochim Acta Part A Mol Biomol Spectrosc.* 2012;95:341–6.

23. Minhas MU, Ahmad M, Ali L, Sohail M. Synthesis of chemically cross-linked polyvinyl alcohol-co-poly (methacrylic acid) hydrogels by copolymerization; a potential graft-polymeric carrier for oral delivery of 5-fluorouracil. *DARU J Pharm Sci.* 2013;21:1–9.

24. Nkhwa S, Fernando Lauriaga K, Kemal E, Deb S. Conference Paper Poly(vinyl alcohol): Physical Approaches to Designing Biomaterials for Biomedical Applications. Hindawi Publ Corp. 2014;1–7.

25. González-Torres M, Leyva-Gómez G, Rivera M, Krötzsch E, Rodríguez-Talavera R, Rivera AL, et al. Biological activity of radiation-induced collagen-polyvinylpyrrolidone-PEG hydrogels. *Mater Lett.* 2017;214:224–7.

26. Vulpe R, Popa M, Picton L, Balan V, Dulong V, Butnaru M, et al. Crosslinked hydrogels based on biological macromolecules with potential use in skin tissue engineering. *Int J Biol Macromol.* 2016;84:174–81.

27. Han W, Zhou B, Yang K, Xiong X, Luan S, Wang Y, et al. Biofilm-inspired adhesive and antibacterial hydrogel with tough tissue integration performance for sealing hemostasis and wound healing. *Bioact Mater.* 2020;5(4):768–78.

28. Rydz J, Šišková A, Andicsová Eckstein A. Scanning Electron Microscopy and Atomic Force Microscopy: Topographic and Dynamical Surface Studies of Blends, Composites, and Hybrid Functional Materials for Sustainable Future. *Adv Mater Sci Eng.* 2019;1–16.

29. Levett PA, Huttmacher DW, Malda J, Klein TJ. Hyaluronic Acid Enhances the Mechanical Properties of Tissue-Engineered Cartilage Constructs. Engler AJ, editor. *PLoS One.* 2014;9(12):1–24.

30. Chouhan D, Mandal BB. Silk biomaterials in wound healing and skin regeneration therapeutics: From bench to bedside. *Acta Biomater.* 2020;103:24–51.

31. Andjelković A, Mordas A, Bruinsma L, Ketola A, Cannino G, Giordano L, et al. Expression of the Alternative Oxidase Influences Jun N-Terminal Kinase Signaling and Cell Migration. *Mol Cell Biol.* 2018;38(24):1–20.

32. Graça MFP, Miguel SP, Cabral CSD, Correia IJ. Hyaluronic acid-Based wound dressings: A review. *Carbohydr Polym.* 2020;241(116364):1–17.

33. Wu S, Deng L, Hsia H, Xu K, He Y, Huang Q, et al. Evaluation of gelatin-hyaluronic acid composite hydrogels for accelerating wound healing. *J Biomater Appl.* 2017;31(10):1380–90.

34. Sharma M, Sahu K, Singh SP, Jain B. Wound healing activity of curcumin conjugated to hyaluronic acid: in vitro and in vivo evaluation. *Artif Cells, Nanomedicine Biotechnol.* 2018;46(5):1009–17.

35. Hang Q, Isaji T, Hou S, Wang Y, Fukuda T, Gu J. A Key Regulator of Cell Adhesion: Identification and Characterization of Important N-Glycosylation Sites on Integrin $\alpha 5$ for Cell Migration. *Mol Cell Biol.* 2017;37(9):1–14.

36. Kamikura DM, Khoury H, Maroun C, Naujokas MA, Park M. Enhanced Transformation by a Plasma Membrane-Associated Met Oncoprotein: Activation of a Phosphoinositide 3'-Kinase-Dependent Autocrine Loop Involving Hyaluronic Acid and CD44. *Mol Cell Biol.* 2000;20(10):3482–96.

37. Grabowska AI, Wilanowski T. FOXN1 Transcription Factor in Epithelial Growth and Wound Healing. *Mol Cell Biol.* 2017;37(17):1–10.